arXiv:cond-mat/0204545v1 [cond-mat.supr-con] 25 Apr 2002

Comment on “Anisotropic s-wave superconductivity in MgB_2”

Todor M. Mishonov,[1, 2, *] Evgeni S. Penev,[2] and Joseph O. Indekeu[1, †]

[1] *Laboratorium voor Vaste-Stoffysica en Magnetisme, Katholieke Universiteit Leuven,*
Celestijnenlaan 200 D, B-3001 Leuven, Belgium
[2] *Department of Theoretical Physics, Faculty of Physics,*
Sofia University “St. Kliment Ohridski”, 5 J. Bourchier Blvd., Bg-1164 Sofia, Bulgaria

An analytical result for renormalization of the jump of the heat capacity $\Delta C/C_N$ by the anisotropy of the order parameter is derived in the framework of the model proposed by Haas and Maki [Phys. Rev. B **65**, 020502(R) (2001)], for both prolate and oblate anisotropy. The graph of $\Delta C/C_N$ versus the ratio of the gaps on the equator and the pole, Δ_e/Δ_p, of the Fermi surface allows a direct determination of the gap anisotropy parameter Δ_e/Δ_p using data from specific heat measurements.

PACS numbers: 74.20.Rp, 74.25.Bt, 74.70.Ad

In a recent Rapid Communication, Haas and Maki[1] discuss a model for the gap anisotropy in MgB_2, a material which has attracted a lot of attention from condensed matter physicists in the past two years. A central issue in this work is to propose an analytic model for analyzing the thermodynamic behavior. Assuming a spherical Fermi surface a simple gap anisotropy function is suggested, $\Delta(\mathbf{k}) \propto 1 + az^2$, where $z = \cos\theta$, and θ is the polar angle. This angular dependence is a natural linear combination of spherical harmonics (Legendre polynomials $P_0(z)$ and $P_2(z)$), and can therefore be interpreted in terms of an s+d model.

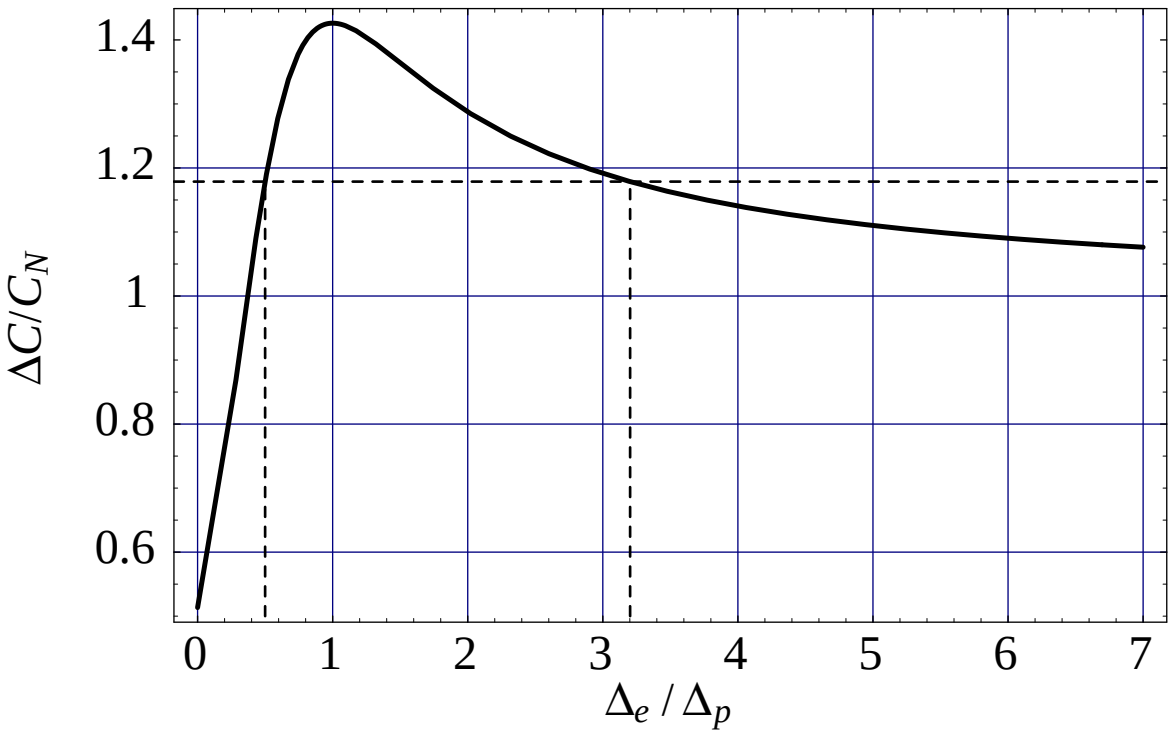

FIG. 1: Jump of the specific heat $\Delta C/C_N$ as function of ratio between “equatorial” and “polar” order parameter Δ_e/Δ_p. For one and the same jump $\Delta C/C_N$ we have prolate and oblate solution.

This model leads to useful results for the temperature dependence of the upper critical field H_{c2} and of the specific heat, which can be fitted to the experimental data, thereby determining the optimal anisotropy parameter a. Note that $a = \Delta_p/\Delta_e - 1$, with $\Delta_p = \Delta(z = 1)$ and $\Delta_e = \Delta(z = 0)$. For example, the dimensionless ratio $\Delta C/C_N$ of the specific heat jump at T_c relative to the normal state specific heat, measured by Wang *et al.*,[2] is a tool for estimating a. Haas and Maki[1] focused on the case $a > 0$.

For oblate-shaped gap anisotropy ($\Delta_e > \Delta_p$), indicated by recent experiments on the critical field anisotropy,[3,4] we take $a < 0$. The sign of a is relevant for this physical property, but irrelevant for the jump of the heat capacity. Note that for $a < -1$ the model gives a gapless superconductor, which is not applicable for MgB_2. Following the weak-coupling BCS approach by the authors[1] we derived the analytic expression

$$\frac{\Delta C}{C_N} = \frac{12}{7\zeta(3)}\frac{1 + 4a/3 + 38a^2/45 + 4a^3/15 + a^4/25}{1 + 4a/3 + 6a^2/5 + 4a^3/7 + a^4/9},$$
$$a = \frac{1}{\Delta_e/\Delta_p} - 1, \qquad \Delta_e/\Delta_p = \frac{1}{1+a} \tag{1}$$

valid for arbitrary a. This expression can be used in experimental data analysis and may lead to *two* solutions (oblate, $a < 0$; prolate, $a > 0$), for a given specific heat jump. The relevant example is shown in Fig. 1.

For the jump $\Delta C/C_N \approx 1.18$ considered by the authors,[1] we recall $a = 1$ and contribute $a = -0.6877$. The corresponding anisotropies are $\Delta_e/\Delta_p = 1/2$ (prolate) and $\Delta_e/\Delta_p = 3.202 > 1$ (oblate solution).

This paper was supported by the Flemish programmes VIS, IUAP and GOA.

---

[*] E-mail: todor.mishonov@fys.kuleuven.ac.be

[†] E-mail: joseph.indekeu@fys.kuleuven.ac.be

[1] S. Haas and K. Maki, Phys. Rev. B **65**, 020502(R) (2001).

[2] Y. Wang, T. Plackowski, and A. Junod, Physica C **355**, 179 (2001).

[3] M. Xu, H. Kitazawa, Y. Takano, J. Ye, K. Nishina, H. Abe, A. Matsushita, N. Tsujii and G. Kido, Appl. Phys. Lett. **79**, 2779 (2001).

[4] M. Angst, R. Puzniak, A. Wisniewski, J. Jun, S.M. Kazakov, J. Karpinski, J. Roos, and H. Keller, Phys. Rev. Lett. **88**, 167004 (2002).